

Persistent and Reversible Phase Control in GdMnO_3 near the Phase Boundary

H. Kuwahara, M. Akaki, J. Tozawa, M. Hitomi, K. Noda,
and D. Akahoshi

Department of Physics, Sophia University, Tokyo 102-8554, Japan

E-mail: h-kuwaha@sophia.ac.jp

Abstract. We have investigated temperature and magnetic-field dependence of dielectric properties in the orthorhombic GdMnO_3 single crystal which is located near the phase boundary between the ferroelectric/spiral-antiferromagnetic phase and the paraelectric/*A*-type-antiferromagnetic one. In this compound, strong phase competition between these two phases results in a unique phase diagram with large temperature and magnetic-field hystereses. Based on the phase diagram, we have successfully demonstrated the persistent and reversible phase switching between them by application of magnetic fields.

1. Introduction

Since the discovery of unusual gigantic magnetoelectric response in orthorhombic TbMnO_3 , a renewed interest has been attracted in magnetoelectric or multiferroic materials from the viewpoint of future device applications such as magnetic- (electric-) field controlled ferroelectric (ferromagnetic) memories or transducers. In this work, we have focused multiferroic GdMnO_3 , because it is located between TbMnO_3 showing the ferroelectric/spiral-antiferromagnetic (FS) phase and EuMnO_3 showing the paraelectric/*A*-type-antiferromagnetic (PA) one [1, 2, 3]. We have simply expected that orthorhombic GdMnO_3 near the phase boundary is suitable to accomplish the phase switching between the FS and PA phases. For the purpose of realizing the phase switching, we have systematically investigated temperature (T) and magnetic-field (H) dependence of dielectric properties of GdMnO_3 single crystal in external magnetic fields along the crystal axes. As a result, we have obtained the detailed magnetoelectric phase diagram of GdMnO_3 in the H - T plane, which is quite complex because there exists a metastable state (hysteretic region) due to the strong phase competition between the FS and PA ones. In this paper, we present a novel persistent and reversible phase control between them by application of magnetic fields.

2. Experiment

The single crystalline sample was grown by the floating zone method. We performed x-ray-diffraction measurement on the resulting crystal at room temperature, and confirmed that the samples have an orthorhombic $Pbnm$ structure without any impurity phases. All specimens used in this study were cut along the crystallographic principal axes into a rectangular shape by means of back-reflection Laue technique. Measurements of temperature and magnetic-field dependence of the dielectric constant and the spontaneous ferroelectric polarization were carried out in a

temperature-controllable cryostat with a superconducting magnet that provided a field up to 8 T. The dielectric constant was measured at 100 kHz with an *LCR* meter (Agilent, 4284 A). The spontaneous polarization was obtained by the accumulation of a pyroelectric current for temperature scans and a displacement current for magnetic-field ones.

3. Results and Discussion

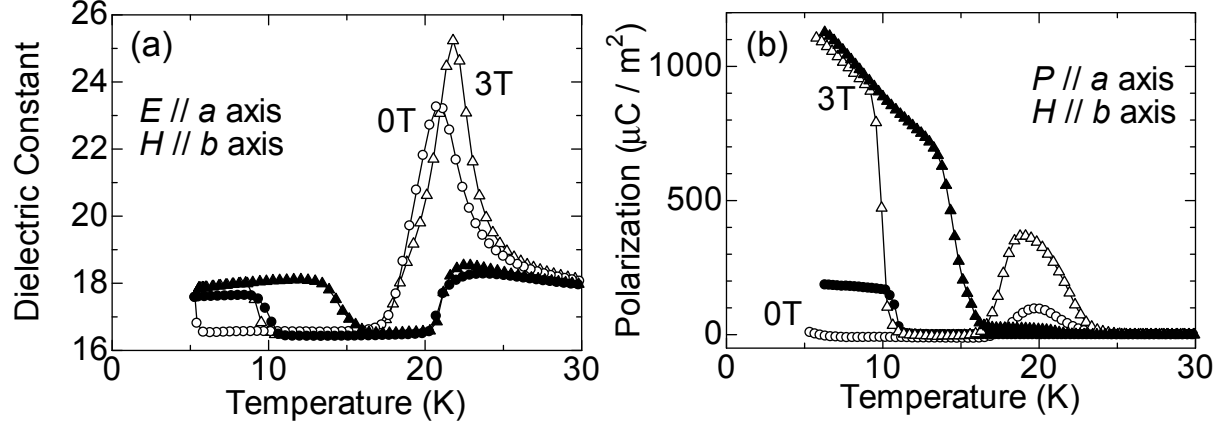


Figure 1. Temperature dependence of dielectric constant ϵ_a (a) and ferroelectric polarization P_a (b) along the *a* axis for GdMnO₃ in a zero magnetic field (circle) and a field of 3 T (triangle). Magnetic field was applied along the *b* axis. Open and solid symbols mean the cooling and warming scans, respectively.

First, we show in Fig. 1 temperature dependence of the dielectric constant along the *a* axis (ϵ_a) and the spontaneous ferroelectric polarization along the same direction (P_a) in fields of zero and 3 T applied along the *b* axis. Data in other field intensities were omitted for clarity. We have confirmed the ferroelectric phase with transition temperatures of 5 K for cooling and 10 K for warming in a zero field. The lowest temperature we can reach is about 5 K, therefore, we can not directly detect P_a for cooling. However, the observed abrupt increase of ϵ_a at 5 K for cooling strongly suggests the phase transition to the ferroelectric state. Because we have observed the simultaneous change of ϵ_a and P_a as clearly shown in the warming scan. Reversal of ferroelectric polarization can also be observed by reversal of poling electric field. Therefore, we have concluded that the ferroelectric phase along the *a* axis exists below 5 K for cooling (10 K for warming) in a zero field [4].

In a temperature range from 17 K to 24 K, one can immediately notice the broad peak of P_a observed for only cooling, which is also an evidence of the ferroelectric phase along the *a* axis. For the cooling scan, a poling electric field of 500 kV/m was applied during the measurement to keep the sample in the single domain state of the ferroelectric phase [5]. The origin of this upper ferroelectric phase is not clear at the present time. We speculate that the upper ferroelectric phase is connected to the lower ferroelectric phase discussed above. The observed reentrant transition, i.e., ferroelectric/spiral-antiferromagnetic (FS) phase $\rightarrow$ paraelectric/*A*-type antiferromagnetic (PA) one $\rightarrow$ FS one, is quite intriguing, however, it is beyond the scope of this paper [6]. Hereafter, we restrict our consideration to the lower ferroelectric phase along the *a* axis.

Let us move on to the magnetic field effect on the ferroelectricity. As already reported in our previous reports [7, 8, 9] and other groups' [1, 2, 10], the magnetic field along the *b* axis (H_b) stabilizes the ferroelectric phase. The observed ferroelectric transition temperatures are

drastically increased by application of H_b , as shown in the Fig. 1 (See also Fig. 2 (a)). On the other hand, magnetic fields along the a and c directions extremely suppress the ferroelectric phase. This is because these magnetic fields (especially H_c) stabilize the canted A -type antiferromagnetic and the resultant paraelectric (PA) phase, which competes and destabilizes the ferroelectric phase with non-collinear spiral spin structures (FS) [1, 2, 6].

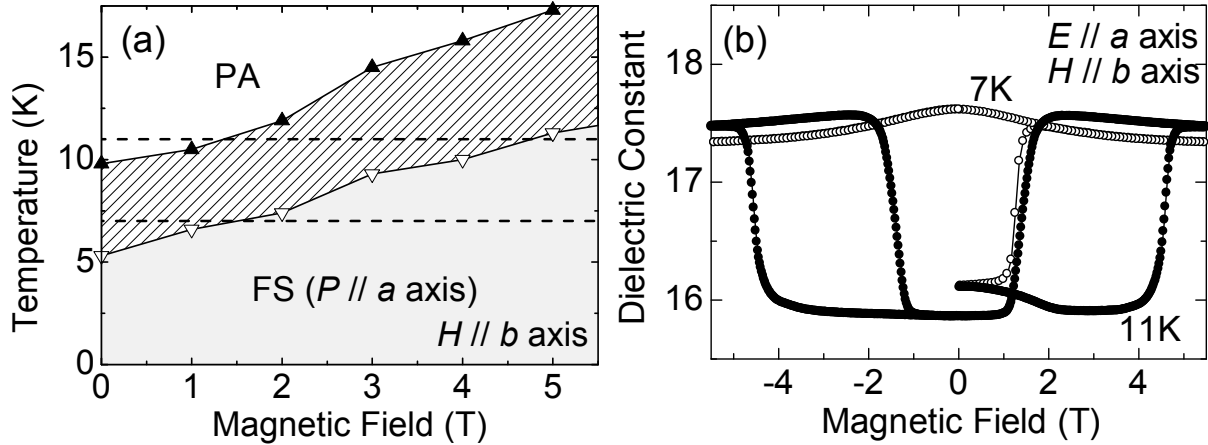


Figure 2. (a) Magneto-electric phase diagram of GdMnO_3 in magnetic fields parallel to the b axis. Hatched area denotes the hysteretic region between the paraelectric/ A -type-antiferromagnetic (PA) and the ferroelectric/spiral-antiferromagnetic (FS) phases. (b) Dielectric constant as a function of applied magnetic fields at fixed temperatures of 7 K and 11 K. Part of the trajectory of the measurements was shown by the dashed lines in (a).

We show in Fig. 2 (a) the magneto-electric phase diagram of GdMnO_3 in the H - T plane, which is determined by the measurements of $\epsilon_a(T)$ in magnetic fields as shown in Fig. 1 (a). Open and solid triangles represent the ferroelectric transition temperatures for the cooling and warming runs, respectively. Hatched area indicates the hysteretic region reflecting the first order nature of the transition. The large hysteretic behavior arises from the strong phase competition between the PA and FS states. This is in sharp contrast to the case of the second-order-like ferroelectric transition in TbMnO_3 and DyMnO_3 , which reside far from the phase boundary between them and have a stable ferroelectric phase with spiral spin structure.

Using the large hysteretic region, we have successfully exemplified the phase switching from the PA phase to the FS one by application of magnetic fields along the b axis. Figure 2 (b) shows an example of such phase switching at two typical temperatures of 7 K and 11 K, which correspond to *within* and *without* the hysteretic region, respectively. (See dashed lines in Fig. 2 (a).) At a temperature of 11 K, the initial low ϵ_a value at a zero field gradually decreases and suddenly jumps up to high ϵ_a state at a field of 4.5 T for the field-increasing scan. As easily noticed from Fig. 1 (a) and (b), low and high ϵ_a states correspond to the PA and FS ones, respectively. The transition magnetic field of 4.5 T at 11 K is in good accordance with the lower phase boundary (open triangles) determined by the $\epsilon_a(T)$ scans in H_b . The high ϵ_a value abruptly drops back to the low one again at 1.5 T for the field-decreasing scan, which indicates the transition from the FS phase back to the PA one again. The transition field also agrees well with the upper phase boundary shown in Fig. 2 (a) (solid triangles). Furthermore, when magnetic fields were applied along the opposite direction ($H_b < 0$), $\epsilon_a(H_b)$ curves show the similar transition from the PA (FS) to the FS (PA) state at the same transition intensity of 4.5 T (1.5 T) for the field-increasing (-decreasing) scan, which is also accompanied by the magnetic-field hysteresis. In this way, we can demonstrate the reversible switching between

the PA and FS states. It should be noted that the ordered (ferroelectric) state is realized by application of magnetic fields. This is in contrast to the magnetic-field destruction of ordered state, e.g., the P_a phase in GdMnO_3 is easily collapsed by the fields along the a and c directions.

After initializing the sample heated well above the transition temperature, we have performed the same $\varepsilon_a(H_b)$ measurement at 7 K which is set *within* the hysteretic region (the lower dashed line in Fig. 2 (a)). The initial low ε_a value at a zero field sharply increases to the high one at a field of 1 T, which means the phase transition from the PA state to the FS one. The transition field was drastically reduced by lowering temperatures, as also seen in Fig. 2 (a). Once the sample has entered the FS state, the FS state subsists against the field-decreasing scan. Moreover, when magnetic fields were applied along the opposite direction like in the case of 11 K, the high ε_a state is completely maintained throughout the field-increasing and -decreasing scans. This second case obviously demonstrates the persistent switching from the PA state to the FS one by application of H_b , which is in contrast to the case of reversible switching at 11 K. To our knowledge, there has been no report on such persistent and reversible phase switching in other orthorhombic RMnO_3 systems. This is partly because other RMnO_3 samples except for the present GdMnO_3 are far from the phase boundary between the PA and FS phases and are stabilized to the FS state *without* the first order nature of the ferroelectric transition.

4. Summary

We have systematically investigated the dielectric properties as a function of temperature and magnetic fields for GdMnO_3 , which is located in the vicinity of the phase boundary between the PA and FS phases. We have deduced the magnetoelectric phase diagram of GdMnO_3 in the H - T plane, and have found the large hysteretic region due to the strong competition between the above two phases. Using the hysteretic region, we have successfully demonstrated the persistent and reversible phase switching between them by application of magnetic fields. This is in sharp contrast to other RMnO_3 systems, which show only reversible phase switching. We believe that these new findings provide the progress towards construction of a magnetic-recording erasable ferroelectric memory.

Acknowledgments

This work was partly supported by Grant-in-Aid for scientific research (C) from the Japan Society for Promotion of Science.

References

- [1] Arima T, Goto T, Yamasaki Y, Miyasaka S, Ishii K, Tsubota M, Inami T, Murakami Y and Tokura Y 2005 *Phys. Rev. B* **72** 100102(R)
- [2] Goto T, Yamasaki Y, Watanabe H, Kimura T and Tokura Y 2005 *Phys. Rev. B* **72** 220403(R)
- [3] Kuwahara H, Noda K, Nagayama J and Nakamura S 2005 *Physica B* **359-361** 1279
- [4] The ferroelectric ground state in a zero field is contradictory to other groups' reports, in which the ferroelectric phase can only exist in the fields along the b axis. This discrepancy arises from the slight difference of oxygen off-stoichiometry. We have checked the reproducibility of the ferroelectricity for several newly-grown samples, which is consistent with our previous works.
- [5] We have confirmed the ordinary pyroelectric current at an upper ferroelectric transition temperature of 24 K for warming without poling electric fields after the sample had been cooled to 20 K (not to the lowest temperature) with poling.
- [6] Detailed magnetic structure has not yet been determined because of the large absorption cross-section of Gd for neutrons. We assume that the ferroelectric phase has presumably the ab spiral spin structures with the commensurate modulation wave vector. The magnetic modulation vector in the ferroelectric phase of GdMnO_3 is reported to be $(0, 1/4, 1)$ (See ref. 1).
- [7] Noda K, Akaki M, Nakamura F, Akahoshi D and Kuwahara H 2007 *J. Phys.: Condens. Matter* **19** 145279
- [8] Noda K, Nakamura S, Nagayama J and Kuwahara H 2005 *J. Appl. Phys.* **97** 10C103
- [9] Noda K, Nakamura S and Kuwahara H 2005 *IEEE Transactions on Magnetics* **41** 2814
- [10] Baier J, Meier D, Berggold K, Hemberger J, Balbashov A and Lorenz T 2006 *Phys. Rev. B* **73** 100402(R)